

Magnetic field - dependent Labusch parameter in LiFeAs superconductor from Campbell penetration depth

Plengchart Prommapan,^{1,2} Makariy A. Tanatar,¹ Bumsung Lee,³
Seunghyun Khim,³ Kee Hoon Kim,³ and Ruslan Prozorov^{1,2,*}

¹The Ames Laboratory, Ames, IA 50011

²Department of Physics & Astronomy, Iowa State University, Ames, IA 50011

³CeNSCMR, Department of Physics and Astronomy,
Seoul National University, Seoul 151-747, Republic of Korea

(Dated: 7 March 2011)

A “true” critical current density, j_c , as opposite to commonly measured relaxed persistent (Bean) current, j_B , was extracted from the Campbell penetration depth, $\lambda_C(T, H)$ measured in single crystals of LiFeAs. The effective pinning potential is non-parabolic, which follows from the magnetic field - dependent Labusch parameter α . At the equilibrium (upon field - cooling), $\alpha(H)$ is non-monotonic, but it is monotonic at a finite gradient of the vortex density. This behavior leads to a faster magnetic relaxation at the lower fields and provides a natural *dynamic* explanation for the fishtail (second peak) effect. We also find the evidence for strong pinning at the lower fields. The inferred field dependence of the pinning potential is consistent with the evolution from strong pinning, through collective pinning and, eventually, to a disordered vortex lattice. The values of $j_c(2\text{ K}) \simeq 2 \times 10^6\text{ A/cm}^2$ provide an upper estimate of the current carrying capability of LiFeAs. Overall, vortex behavior of almost isotropic, fully-gapped LiFeAs is very similar to highly anisotropic d-wave cuprate superconductors, the similarity that requires further studies in order to understand unconventional superconductivity in cuprates and pnictides.

PACS numbers: 74.25.Ha, 74.25.Op, 74.70.Xa, 74.70.Ad

The determination of the critical current density j_c , is one of the fundamental problems in the vortex physics of type-II superconductors. Not only it is important for the assessment of the current-carrying capabilities relevant for practical applications, but knowing “true” j_c is needed to understand microscopic mechanisms of vortex pinning. What is often called “critical current” is routinely determined from conventional DC magnetization measurements, alas this quantity is a convolution of “true” j_c and magnetic relaxation during the characteristic time, Δt , of the experiment. For example, in case of ubiquitous *Quantum Design* MPMS (SQUID) magnetometry, $\Delta t \geq 10\text{ sec}$. We will call measured supercurrent j_B to distinguish it from the “true” j_c that is achieved when the vortices are de-pinned by the Lorentz force. By definition, j_c is reached when the energy barrier for vortex motion vanishes, $U(j_c) = 0$, whereas the measured current density j_B is determined by $U(j_B) = k_B T \ln(1 + \Delta t/t_0)$, where $t_0 \lesssim 1\text{ }\mu\text{sec}$ is the characteristic time scale that depends on both sample geometry and details of pinning [1–5]. This also results in a quite different temperature dependence of $j_B(T)$ compared to $j_c(T)$. Another approach to measure critical current density is to use AC susceptibility. Conventional time-domain susceptometers operate at frequencies $f \lesssim 10\text{ kHz}$ (hence $\Delta t \gtrsim 0.1\text{ msec}$) and have large driving amplitudes, $H_{ac} \gtrsim 0.1\text{ Oe}$. Such perturbation displaces vortices from the potential wells and one can use harmonics analysis to determine frequency - dependent current density, $j_B(T, B, f)$. This technique has been applied in both global [6] and local [7, 8] forms.

In Fe-based superconductors flux creep is substantial at all temperatures, thus measured j_B is expected to be lower than j_c . Indeed, reports produce only moderate current densities, $j_B \lesssim 10^6\text{ A/cm}^2$, - unusual for low-anisotropy high- T_c materials [9–15].

To access the information about pinning potential itself, one needs to measure the linear response when vortices are not driven out of the pinning potential wells. One way to do this is to measure so-called Campbell penetration depth which determines how far a small AC magnetic field penetrates the superconductor in the presence of vortices (induced by static external magnetic field) in the limit of $H_{ac} \rightarrow 0$, when vortex response is purely elastic and linear [16–18]. For a pinning potential, $V(r)$, the vortex displacement from the equilibrium position due to small H_{ac} is found from $dV/dr = f_L$, where the Lorentz force, $f_L = j \times \phi_0/c$. Maximum force determines the “true” critical current density, $j_c = c\alpha r_p/B$, attained at the range of the pinning potential r_p . If vortex distribution is inhomogeneous, static (Bean) current [19], j_B , is superimposed with the excitation AC current and the response is determined by the effective Labusch constant $\alpha(j_B) \equiv d^2V/dr^2|_{r=r_0}$. Clearly $\alpha(j_B)$ is constant only for a parabolic $V(r)$. The Campbell penetration depth is given by $\lambda_C^2 = \phi_0 B / (4\pi\alpha(j_B))$ [16–18, 20].

Consider a typical experiment, which we use in the following. Sample is cooled in zero magnetic field and then static magnetic field is applied. This creates a gradient of vortex density supported by the persistent Bean current density j_B [19]. Small-amplitude H_{ac} causes vor-

tex vibrations within pinning potential well, a condition for Campbell penetration depth measurements [16–18, 20]. After the sample is warmed above T_c it is cooled again keeping external static field constant (field-cooling) whence $j_B = 0$. We therefore may expect some hysteresis with $\lambda_{C,ZFC} > \lambda_{C,FC}$ if $V(r)$ is non-parabolic. Therefore, by measuring zero field - cooled (zfc) field-cooled (fc) λ_C at different magnetic fields and temperatures we can estimate “true” $j_c(H, T)$ and access the information regarding shape of the pinning potential. For more details the reader is referred to earlier studies of high $-T_c$ cuprates [20].

One of the most interesting and commonly observed features of unconventional superconductors is so-called second magnetization peak (also known as “fishtail”) [3]. It has now been observed in most Fe-based superconductors when magnetic field is aligned parallel to the crystallographic c -axis [9, 10, 12–15, 21]. The origin of fishtail can be static, i.e., when “true” $j_c(H)$ is a non-monotonic function of field, H , or it can be dynamic caused by field-dependent magnetic relaxation [5, 22]. Experimental determination of the origin of the fishtail in each material is, thus, very important as it allows to shed light on the nature of the flux pinning, hence defect structure “seen” by the Abrikosov vortices. In Fe-based superconductors, the interest is further fueled by multiple reports that defects, even non-magnetic, are pair-breaking due to, presumably, unconventional $s_{\pm}$ symmetry of the order parameter [23, 24]. Additionally, it seems that low-field behavior of most pnictides is governed by the so-called strong pinning, which results in a sharp peak in magnetization at $H \rightarrow 0$ [21]. Therefore, to conduct a clean, baseline experiment, one ideally needs Fe-based superconductor with reduced scattering. These materials are rare, but do exist in form of only few stoichiometric compounds, LiFeAs being one of them. Due to high sensitivity to air and moisture, there are only few reports on the vortex properties in LiFeAs crystals. Fishtail effect and relatively high j_B (5 K) $\approx 1 \times 10^5$ A/cm² were found in Ref.[15], whereas much lower j_B (5 K) $\approx 1 \times 10^3$ A/cm² was reported in Ref.[25]. Such spread may be related to clean - limit superconductivity in this compound when even small variation of impurity concentration causes significant change in the persistent current density and magnetic relaxation.

In this paper we report measurements of Campbell penetration depth in single crystals of LiFeAs. We show that the fishtail has dynamic origin and the field-dependent magnetic relaxation is due to transformation of the pinning potential with field. Namely, Labusch constant (and “true” critical current, $j_c(H)$) is a monotonic function of field when Bean current (macroscopic vortex density gradient) is present, but it becomes a non-monotonic function of field at a homogeneous distribution of vortices. The values of j_c (2 K) $\approx 1.8 \times 10^6$ A/cm² provide upper estimate of the current carrying capabil-

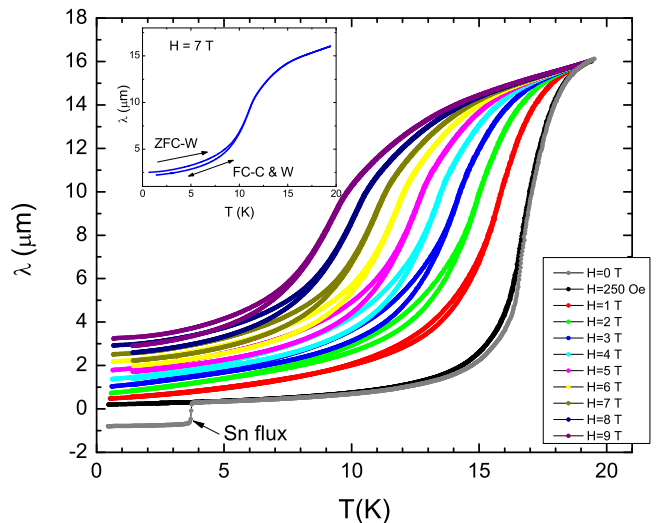


FIG. 1. (Color online) Magnetic penetration depth measured in a ZFC-FC process at different fields. $H = 0$ curve shows a step due to leftovers of Sn flux. It was quenched by applying a $H = 250$ Oe field. Inset shows an example of the hysteresis of $\lambda_C(T)$ at $H = 7$ T.

ity of this material and show the significance of magnetic relaxation. We also find evidence for the strong pinning regime at the low fields. With the increase of the magnetic field vortex pinning and creep change to a collective regime and, finally, cross over to another vortex state, perhaps dominated by plastic deformations. Despite being quite different from high- T_c cuprates in terms of pairing and gap structure, it seems that vortex behavior of Fe-based superconductors is remarkably similar to high- T_c materials.

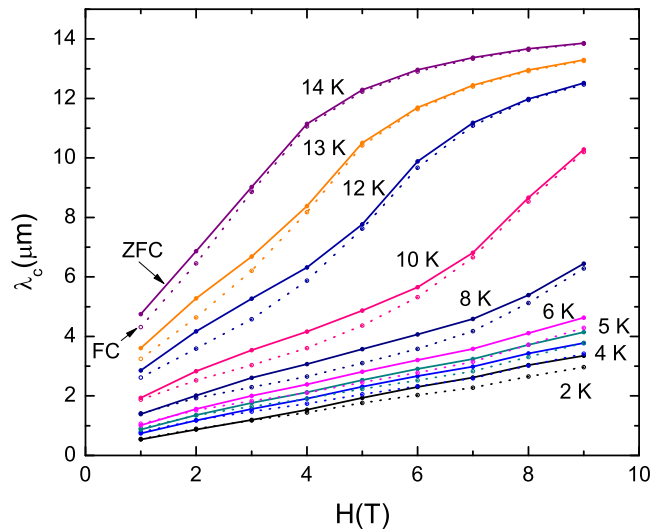


FIG. 2. (Color online) Campbell penetration depth as function of magnetic field at different temperatures extracted from the data of Fig. 1. Solid lines - ZFC and dashed lines are FC data.

Single crystals of LiFeAs were grown out of Sn flux as described in detail elsewhere [26] and were transported for measurements in sealed ampoules. Immediately after opening, $(0.5 - 1) \times (0.5 - 1) \times (0.1 - 0.3) \text{ mm}^3$ samples were placed into the cryostat for the measurements. Additionally, samples were extensively characterized by transport and magnetization measurements [26]. Zero-field transition temperature of our samples was about, $T_c \approx 18 \text{ K}$. The magnetic penetration depth was measured with the tunnel - diode resonator technique (for review, see [27]). The sample was inserted into a 2 mm diameter copper coil that produced an rf excitation field (at $f \approx 14 \text{ MHz}$) of $H_{ac} \sim 20 \text{ mOe}$. An external DC magnetic field ($0 - 9 \text{ T}$) was applied parallel to the AC field, both parallel to the c -axis, $H_{ac} \parallel H \parallel c$ -axis. The shift of the resonant frequency (in cgs units) is given by $\Delta f(T) = -G4\pi\chi(T)$, where $\chi(T)$ is the differential magnetic susceptibility, $G = f_0 V_s / 2V_c(1 - N)$ is a calibration constant, N is the demagnetization factor, V_s is the sample volume and V_c is the coil volume. The constant G was determined from the full frequency change by physically pulling the sample out of the coil. With the characteristic sample size, R , $4\pi\chi = (\lambda/R) \tanh(R/\lambda) - 1$, from which $\Delta\lambda$ can be obtained [27, 28]. The measured penetration depth consists of two terms, London penetration depth and Campbell penetration depth, $\lambda_m^2 = \lambda_L^2 + \lambda_C^2$ [17]. We determined $\lambda_L(T)$ from the measurements at $H = 0$.

Figure 1 shows magnetic penetration depth measured upon warming, after sample was cooled in zero field and target field was applied at low temperature (ZFC-W) compared to the measurements upon cooling when target field was fixed above T_c and kept constant (FC-C). A step at low temperatures on a $H = 0$ curve is due to residual Sn flux. It was quenched by applying a moderate $H = 250 \text{ Oe}$ field, which does not affect our analysis of the much higher fields. Inset in Figure 1 shows an example of the magnetic hysteresis measured at $H = 7 \text{ T}$ (notice that once ZFC-W process was complete, subsequent warming-cooling measurements (FC-C and FC-W) resulted in the same curve indicating homogeneous vortex distribution). The hysteresis between ZFC-W and FC-C-W is much smaller then, for example, observed in BSCCO crystals [20], which is most likely due to much more 3D electronic nature of LiFeAs. From the measured penetration depth in zero field, $\lambda_L(T)$, and the one measured in applied magnetic field, $\lambda_m(T, H)$, we determine the Campbell penetration depth via, $\lambda_C = \sqrt{\lambda_m^2 - \lambda_L^2}$ as shown in Fig.2.

From the Campbell penetration depth we determine the “true” critical current density as, $\frac{4\pi}{c}j_c = r_p\phi_0/\lambda_C^2$ were we assumed the radius of the pinning potential be a coherence length, $r_p \simeq \xi \simeq 7 \text{ nm}$ [29]. Figure 3 shows j_c as a function of temperature at different magnetic fields determined after ZFC-W process (top frame) and FC-C process (bottom frame). In both cases, the curves

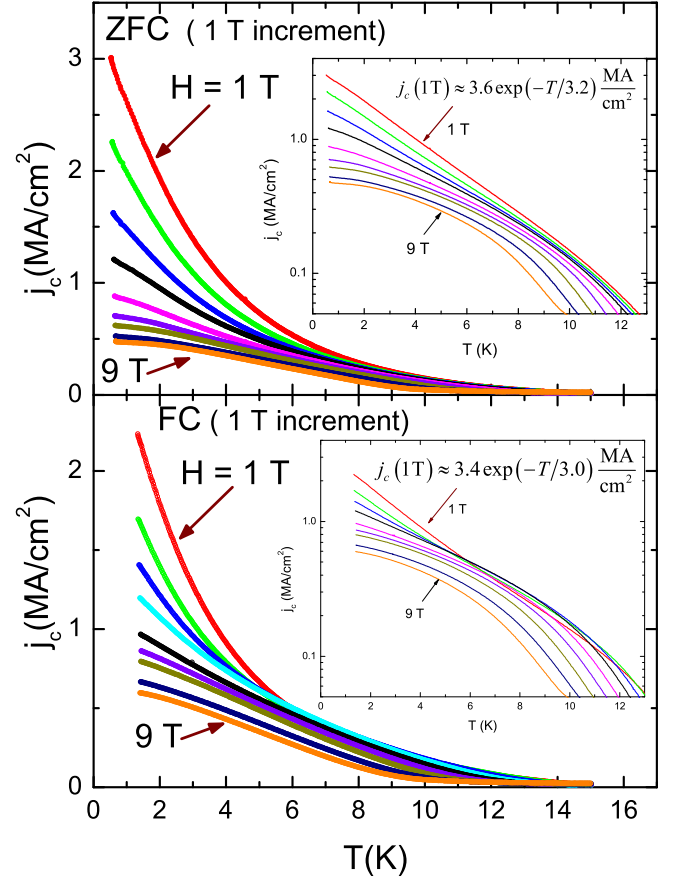


FIG. 3. (Color online) “true” critical current density, j_c , determined from the ZFC (top frame) and FC (bottom frame) experiments at indicated values of the applied external magnetic fields. Insets show semi-log plots indicating exponential dependence of j_c at lower fields and a crossover to a different pinning regime at the higher fields.

are monotonic in temperature and show substantial temperature dependence similar to high $-T_c$ cuprates, reinforcing the earlier statement that vortex properties of Fe-based superconductors are remarkably similar to the cuprates, despite the difference in dimensionality of the electronic structure [30].

To understand the functional dependence, we plot determined $j_c(T)$ on a semi-logarithmic plot as shown in the insets in Fig. 3. At relatively low fields, the behavior is very similar to the earlier reports of strong pinning [21] and can be well approximated by the exponential temperature dependence, $j_c(1 \text{ T}) \simeq 3.4 \exp(-T/3.0) \text{ MA/cm}^2$ for FC-C process and $j_c(1 \text{ T}) \simeq 3.6 \exp(-T/3.2) \text{ MA/cm}^2$ for ZFC-W measurements. This very similar behavior imply that strong pins result in a more-or less parabolic $V(r)$ and are practically independent of the bias Bean current, j_B . However, at the higher fields, the critical current becomes less temperature dependent, probably due to saturation of strong pins and a crossover first to the collective pinning regime and eventually to the

disordered lattice dominated by plastic deformations.

Finally, Fig.4 shows “true” critical current density, j_c , determined from ZFC Campbell penetration depth (top frame) and from the FC Campbell penetration depth (bottom frame) as a function of magnetic field at different temperatures. While ZFC curves are monotonic, a clear fishtail signature is observed in the equilibrium FC-C-W measurements at higher temperatures. The inset in Fig.4 emphasizes this result.

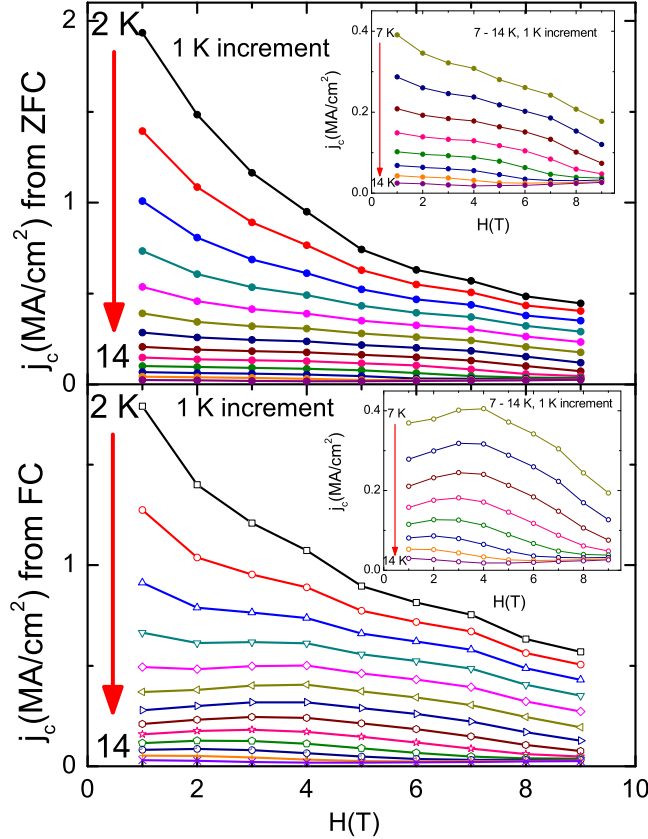


FIG. 4. (Color online) Critical current density determined from ZFC Campbell penetration depth (top frame) and from the FC Campbell penetration depth (bottom frame) showing the absence of the fishtail magnetization in the former and its presence in the latter.

Our results can be interpreted in the following way. Maximum critical current values, $j_c(2\text{ K}) \approx 1.8 \times 10^6\text{ A/cm}^2$, show that conventional measurements underestimate critical currents, probably due to significant magnetic relaxation. However, the most striking result is that j_c , obtained in a non-equilibrium ZFC process, is monotonic with magnetic field at all temperatures, whereas equilibrium j_c shows a clear signature of the fishtail (second peak) magnetization. Since conventional (relaxed) DC measurements show fishtail [15], we conclude that fishtail effect is of dynamic origin and results from bias (Bean) current - dependent Labusch constant, $\alpha(j_B)$. At the critical current density magnetization

is a monotonic function of the magnetic field. However, vortex distribution relaxes at much faster rates at smaller fields and higher temperatures. During this relaxation the effective vortex pinning potential transforms, probably indicating collective effects and ultimately a crossover to the disordered vortex lattice. In the experiment, it shows as a non-monotonic field dependence of the Labusch parameter, $\alpha(j_B = 0, H)$. It is possible that fishtail has similar static and dynamic origin in high-temperature cuprates and a very interesting question is how to reconcile very different electronic properties of Fe-based superconductors and quite similar vortex behavior.

We thank Kees van der Beek, Marcin Konczykowski and Alexey Koshelev for useful discussion. The work at Ames Laboratory was supported by the U.S. Department of Energy, Office of Basic Energy Sciences, Division of Materials Sciences and Engineering under contract No. DE-AC02-07CH11358. Work at SNU was supported by National Creative Research Initiative (2010-0018300). R.P. acknowledges support from the Alfred P. Sloan Foundation.

* Corresponding author: prozorov@ameslab.gov

- [1] V. B. Geshkenbein and A. I. Larkin, Zh. Eksp. Teor. Fiz. **95**, 1108 (1989) [Sov. Phys. JETP **68**, 639 (1989)].
- [2] V. M. Vinokur, M. V. Feigel'man, and V. B. Geshkenbein, Phys. Rev. Lett. **67**, 915 (1991).
- [3] G. Blatter, M. V. Feigel'man, V. B. Geshkenbein, A. I. Larkin, and V. M. Vinokur, Rev. Mod. Phys. **66**, 1125 (1994).
- [4] Y. Yeshurun, A. P. Malozemoff, and A. Shaulov, Rev. Mod. Phys. **68**, 911 (1996).
- [5] L. Burlachkov, D. Giller, and R. Prozorov, Phys. Rev. B **58**, 15067 (1998).
- [6] S. Shatz, A. Shaulov, and Y. Yeshurun, Phys. Rev. B **48**, 13871 (1993).
- [7] R. Prozorov, A. Shaulov, Y. Wolfus, and Y. Yeshurun, J. Appl. Phys. **76**, 7621 (1994).
- [8] R. Prozorov, A. Shaulov, Y. Wolfus, and Y. Yeshurun, Phys. Rev. B **52**, 12541 (1995).
- [9] R. Prozorov, N. Ni, M. A. Tanatar, V. G. Kogan, R. T. Gordon, C. Martin, E. C. Blomberg, P. Prommapan, J. Q. Yan, S. L. Bud'ko, and P. C. Canfield, Phys. Rev. B **78**, 224506 (2008).
- [10] H. Yang, C. Ren, L. Shan, and H.-H. Wen, Phys. Rev. B **78**, 092504 (2008).
- [11] H. Yang, H. Luo, Z. Wang, and H.-H. Wen, Appl. Phys. Lett. **93**, 142506 (2008).
- [12] R. Prozorov, M. E. Tillman, E. D. Mun, and P. C. Canfield, New J. Phys. **11**, 035004 (2009).
- [13] H.-J. Kim, Y. Liu, Y. S. Oh, S. Khim, I. Kim, G. R. Stewart, and K. H. Kim, Phys. Rev. B **79**, 014514 (2009).
- [14] B. Shen, P. Cheng, Z. Wang, L. Fang, C. Ren, L. Shan, and H.-H. Wen, Phys. Rev. B **81**, 014503 (2010).
- [15] A. K. Pramanik, L. Harnagea, C. Naeke, A. U. B. Wolter, S. Wurmehl, V. Kataev, and B. Büchner, arXiv:1009.4896 (2010), NoStop

- [16] E. H. Brandt, Phys. Rev. Lett. **67**, 2219 (1991).
- [17] E. H. Brandt, Rep. Prog. Phys. **58**, 1465 (1995).
- [18] A. Koshchev and V. Vinokur, Physica C **173**, 465 (1991).
- [19] C. P. Bean, Rev. Mod. Phys. **36**, 31 (1964).
- [20] R. Prozorov, R. Giannetta, N. Kameda, T. Tamegai, J. Schlueter, and P. Fournier, Phys. Rev. B **67**, 1845011 (2003).
- [21] C. J. van der Beek, G. Rizza, M. Konczykowski, P. Fertey, I. Monnet, T. Klein, R. Okazaki, M. Ishikado, H. Kito, A. Iyo, H. Eisaki, S. Shamoto, M. E. Tillman, S. L. Bud'ko, P. C. Canfield, T. Shibauchi, and Y. Matsuda, Phys. Rev. B **81**, 174517 (2010).
- [22] G. P. Mikitik and E. H. Brandt, Phys. Rev. B **64**, 184514 (2001),.
- [23] V. G. Kogan, Phys. Rev. B **80**, 214532 (2009).
- [24] R. T. Gordon, H. Kim, M. A. Tanatar, R. Prozorov, and V. G. Kogan, Phys. Rev. B **81**, 180501 (2010).
- [25] Y. J. Song, J. S. Ghim, B. H. Min, Y. S. Kwon, M. H. Jung, and J.-S. Rhyee, App. Phys. Lett. **96**, 212508 (2010).
- [26] B. Lee, S. Khim, J. S. Kim, G. R. Stewart, and K. H. Kim, Europhys. Lett. **91**, 67002 (2010),.
- [27] R. Prozorov and R. W. Giannetta, Supercond. Sci. Technol. **19**, R41 (2006).
- [28] R. Prozorov, R. Giannetta, A. Carrington, and F. Araujo-Moreira, Phys. Rev. B **62**, 115 (2000).
- [29] D. S. Inosov, J. S. White, D. V. Evtushinsky, I. V. Morozov, A. Cameron, U. Stockert, V. B. Zabolotnyy, T. K. Kim, A. A. Kordyuk, S. V. Borisenko, E. M. Forgan, R. Klingeler, J. T. Park, S. Wurmehl, A. N. Vasiliev, G. Behr, C. D. Dewhurst, and V. Hinkov, Phys. Rev. Lett. **104**, 187001 (2010).
- [30] M. A. Tanatar, N. Ni, C. Martin, R. T. Gordon, H. Kim, V. G. Kogan, G. D. Samolyuk, S. L. Bud'ko, P. C. Canfield, and R. Prozorov, Phys. Rev. B **79**, 094507 (2009).